

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/378929572>

Performance of Black Cotton Soil Stabilized with Silica Sand and Lime for Use as Road Subgrade

Article · February 2024

DOI: 10.14445/23488352/JJCE-V11I12P102

CITATIONS

0

READS

82

3 authors, including:



[Clementine Akimana](#)

Pan African University

1 PUBLICATION 0 CITATIONS

SEE PROFILE

Original Article

Performance of Black Cotton Soil Stabilized with Silica Sand and Lime for Use as Road Subgrade

Akimana Clementine¹, Samuel Waweru², Isaac Fundi Sanewu³

¹Department of Civil Engineering, Pan African University Institute for Basic Sciences, Technology and Innovation, Jomo Kenyatta University of Agriculture and Technology, Nairobi, Kenya.

²Department of Civil & Structural Engineering, Masinde Muliro University of Science and Technology, Nairobi, Kenya.

³Department of Construction Management, Jomo Kenyatta University of Agriculture and Technology, Nairobi, Kenya.

¹Corresponding Author : akicle22@gmail.com

Received: 04 December 2023

Revised: 05 January 2024

Accepted: 06 February 2024

Published: 29 February 2024

Abstract - Designing foundations, particularly highway pavements, on black cotton soil has consistently posed a delinquent for engineers, as structures supported by this type of black cotton soil are prone to unexpected cracking and settlement. The issue this study aims to solve is the lack of appropriate performance materials for use as road subgrade in regions with black cotton soil. This study aims to inspect if a mixture of silica sand and lime can be used to advance the mechanical properties of black cotton soil, thereby improving its performance for road subgrade construction. The initial step involves evaluating natural soil's qualities using various tests such as Unconfined Compressive Strength (UCS), Atterberg limits, Californian Bearing Ratio (CBR), and Compaction tests. Subsequently, the soil sample is blended with silica sand in incremental amounts ranging from 0% to 12% of the soil sample's dry weight at intervals of 2%. Through this experimentation, it was determined that the ideal amount of silica sand for treating the soil is 8%. At this content level, the corresponding values for UCS and soaked CBR were 181.23 kPa and 6.9%, respectively. The results obtained did not meet the targeted strength; hence, it was necessary to add some lime content in order to meet the targets. After adding lime in steps of 2%, the characteristics of targeted strengths were met at 2% inclusion of lime, and the corresponding soaked CBR and UCS values were 12.3 % and 188.39 kPa, respectively. These values were in line with the recommended standard for treated soil characteristics to be used in subgrade material. In conclusion, an optimal mixture of 8% silica sand and 2% lime is selected.

Keywords - Black cotton clay soil, Road subgrade, Lime, Silica sand, Stabilization.

1. Introduction

The development of transportation infrastructure is widely recognized as a significant driver of growth, as exemplified by the saying, "Wherever a road is built, progress follows." [1] Developing road infrastructure is imperative for empowering rural communities' economic and social progress in Africa by extending reach to markets, health care, education, and other basic amenities and services.

African countries, in the process of growth and advancement, present a substantial challenge for governments seeking to enhance road connectivity due to typically high construction costs. Connectivity helps link underserved populations to essential resources and opportunities that can alleviate hardship and support community thriving [2].

Black cotton soils expand and contract with changes in moisture content. When they absorb water during the rainy season, they swell and exert upward pressure, potentially causing damage to structures constructed on them [3].

On the other hand, during dry seasons, they lose water and contract, creating voids even without external loads. The most substantial damage occurs when there are frequent fluctuations in moisture content. To tackle the challenges posed by expansive clay soils, various treatment approaches have been proposed. These methods encompass adjusting the road design to align with the particular site conditions, the substitution and removal of existing soil materials, and the application of soil stabilization techniques.

Clay soil has been previously used as the subgrade or base material to construct roads [4]. With evolving requirements and a growing scarcity of suitable soils, black cotton soils are finding increased utilization in several civil engineering applications [5].

Lime and cement emerge as the predominant stabilizing materials for soil. Moreover, the use of such calcium-based additives faces growing concerns about Carbon Dioxide (CO₂) emission and climate change.



Therefore, there is a need for more sustainable soil stabilization techniques [6, 7]. The issue of soil stabilization presents a pressing challenge, necessitating the exploration of innovative, cost-effective approaches and stabilizing agents that align with global goals [8].

Nevertheless, these materials exhibit inadequate performance when subjected to challenging traffic and moisture conditions, especially if they have a lot of clay in them, which can lead to swelling or cracking [9]. Therefore, in some cases, especially in road construction, there is a need to stabilize these materials before application.

Research has shown that lime can strengthen the mechanical and physical characteristics of soils, making it a potentially effective stabilizing agent for black cotton soils [10]. Nevertheless, the suitability of these materials for stabilizing black cotton soils for subgrade construction is not well understood [11]. Therefore, it is necessary to investigate the performance of silica sand and lime when used as stabilizing agents for these soils.

Hydrated lime (Calcium Hydroxide, $\text{Ca}(\text{OH})_2$), Quicklime (Calcium Oxide, CaO), or lime slurry can be employed for the purpose of stabilizing clay soils. Hydrated lime is produced through the chemical reaction between Quicklime and water [12].

The stabilization of clay with lime results in long-lasting changes to its properties. Lime and wet clay react in a number of ways, including pozzolanic reaction, cation exchange, and carbonation [13]. The exchange of cation is accountable for the accumulation of soil fragments, which ensues in early strength development. The slow-moving pozzolanic response is what leads to development at the late strength.

According to references [14, 15], Silica Dioxide (SiO_2) is the predominant mineral composition of quartz, which makes up the majority of the tiny particles or grains of rock and minerals that make up silica sand. This composition makes silica sand rich in silica, which is crucial for soil stabilization [16]. Silica sand is widely utilized due to its physical and chemical characteristics. It finds applications in various industries, including glass production, foundries for casting molds, ceramics, shale hydrocarbon extraction, polymers, paints, rubber, water filtration, and more [17].

Incorporating silica sand as an admixture in soil stabilization applications has shown improved strength performance and the utilization of locally available materials for sustainable subgrade road construction. Though many researchers focused on the characteristics of stabilized clay soil (black cotton) with lime, only a few have attempted to investigate a blend of silica sand with lime to stabilize black cotton soil.

This study aims to use silica sand combined with lime-stabilized black cotton soil to optimize mix proportions and improve mechanical properties for stabilized subgrade road construction.

2. Materials and Methods

2.1. Materials

The study included silica sand, lime, and black cotton clay soil as its materials. The black cotton soil was sourced from the Juja area of Kiambu County, Kenya. The silica sand and hydrated lime were purchased locally (Kenya). Silica sand was crashed and then sieved using a 0.6mm BS sieve before being used.

2.2. Sample Preparation

The samples of hydrated lime, silica sand, and black cotton soil were taken to the Kenya Ministry of Mining laboratory in Nairobi for chemical analysis. The material's chemical composition was ascertained using the X-Ray Fluorescence (XRF) analysis. This was done to gain a more profound understanding of how silica sand and lime could potentially interact chemically when blended with black cotton soil.

X-Ray Diffraction (XRD) analysis was used to determine the oxide compositions of lime, silica sand, and black cotton soil were described. However, the materials were sieved through a 75 μm sieve before being scanned in an X-Ray Diffractometer (XRD) apparatus using the DB PHASER portable XRD equipment to estimate the molecular composition of the material. As the X-rays activated the sample, it produced variable-frequency diffraction peaks when it was scanned in the XRD device. Using the peaks of the X-ray emission spectra, the various compounds in the samples were identified.

The engineering properties included particle size distribution, specific gravity, moisture content, consistency limits, and free swell, which were performed according to British Standard BS1377:1990, ASTM-962-15, ASTM D-423-61T/D424-59/854. Additionally, the soil was categorized according to the guidelines of the Unified Soil Classification System (USCS). AASHTO M145-91 and BS 1377-1924-13 and 15, ASTM D2487.

The black cotton soil was treated with varying amounts of silica sand at 0%, 2%, 4%, 6%, 8%, 10% and 12% of the dry weight of the soil sample. The optimum amount of silica sand that had the highest performance was then selected. The soil was further treated using lime varying at 0%, 2%, 4%, 6%, and 8% blended with the optimum percentage of silica sand (Figure 1). The Atterberg limits, compaction, free swell, Unconfined Compression Strength (UCS), and California Bearing Ratio (CBR) tests were performed according to standard procedures.

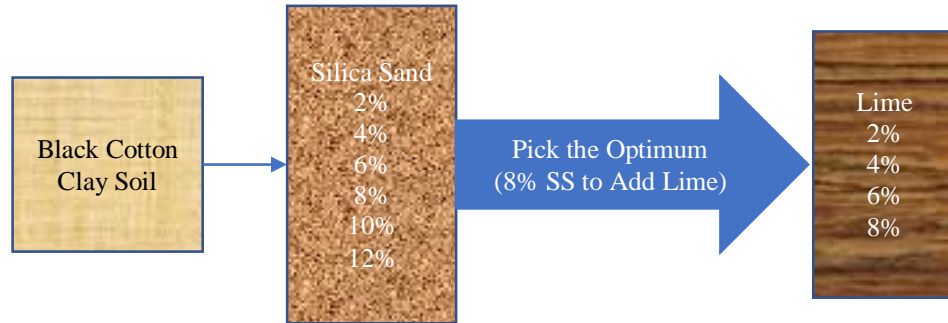


Fig. 1 Schematic layout of treatment of black cotton soil

3. Results and Discussion

3.1. Chemical Characterization of Black Cotton Soil, Silica Sand, and Lime

The X-Ray Fluorescence (XRF) analysis findings for the samples are shown in Table 1. The analysis revealed that the black cotton soil was primarily composed of Silica (SiO_2) and contained a notable amount of iron oxide. This composition suggests that the presence of swelling clay minerals could cause shrink-swell behavior like smectite and illite, which are rich in iron. On the other hand, as indicated in Table 1, silica sand was predominantly composed of Silicon Dioxide (SiO_2) at 96.080%.

In the case of lime, calcium oxide exhibited the highest content, followed by aluminum and iron oxide, as shown in Table 1. According to the chemical characterization, there may be a way to improve metal cation exchange, which would take the place of the expanded clay minerals' drained double layer and improve flocculation, as suggested by [19]. The elemental makeup of lime results in the creation of gels such as Calcium Silicate Hydrate (CSH), Calcium Aluminate Hydrate (CAH), and Calcium Alumina Silicate Hydrate (CASH). These amorphous gels undergo crystallization over time, which involves the production of cementitious compounds that successfully combine clay particles [20].

Table 1. The chemical composition of the silica sand, black cotton, and lime

Oxides	Amount Oxides in Clay Soil Black Cotton (%)	Amount Oxides in Lime (%)	Amount Oxides in Silica Sand (%)
Magnesium Oxide (MgO)	-	3.393	1.148
Aluminium Oxide (Al_2O_3)	9.883	2.550	1.491
Silica (SiO_2)	78.543	-	96.080
Phosphorus Pentoxide (P_2O_5)	-	0.696	0.094
Sulphur (S)	-	0.647	-
Chlorine (Cl)	-	-	-
Potassium Oxide (K_2O)	0.652	-	0.340
Calcium Oxide (CaO)	1.347	92.262	0.287
Titanium (Ti)	0.931	0.045	0.022
Chromium (Cr)	-	-	-
Manganese (Mn)	0.535	0.027	0.009
Iron Oxide (Fe_2O_3)	7.752	0.300	0.517
Copper (Cu)	0.004	0.031	0.002
Zinc (Zn)	0.017	-	0.002
Strontium (Sr)	0.014	0.026	-
Zirconium (Zr)	0.117	0.003	0.003

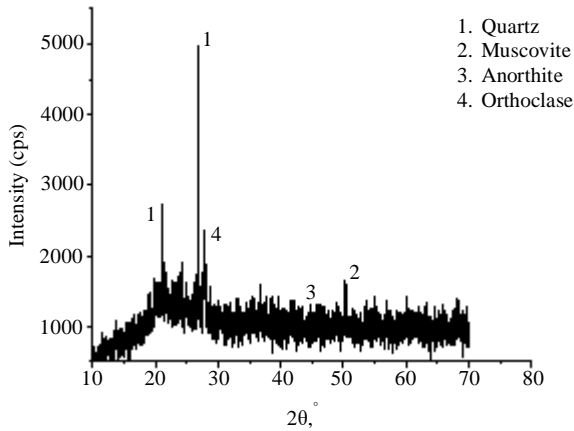


Fig. 2 X-Ray Diffractogram (XRD) patterns of black cotton

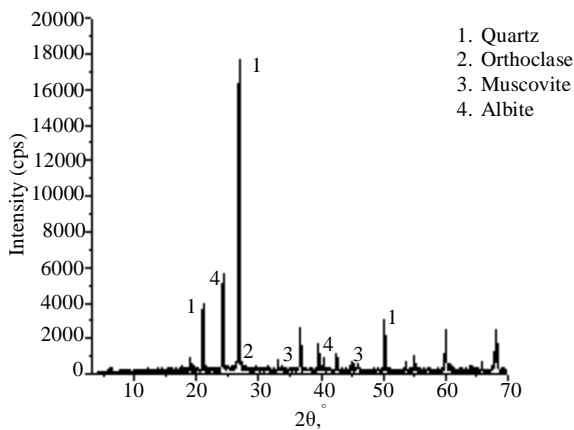


Fig. 3 X-Ray Diffractogram (XRD) patterns for silica sand

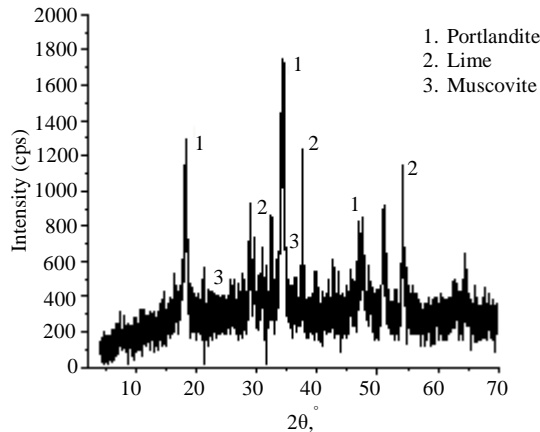


Fig. 4 X-Ray Diffractogram (XRD) patterns of Lime

Analyses using XRD were performed on processed Black Cotton (BC), Silica Sand (SS), and lime to determine the mineralogical properties of these materials, as illustrated in (Figures 2, 3, and 4) respectively. The results showed that both BC and SS contained significant quantities of quartz, which is consistent with the observations made by [21, 18]. Muscovite and orthoclase were similarly detected in substantial amounts in both BC and SS.

Furthermore, the lime sample exhibited the presence of portlandite, which aligns with the results obtained from the chemical composition analysis as reported by [22].

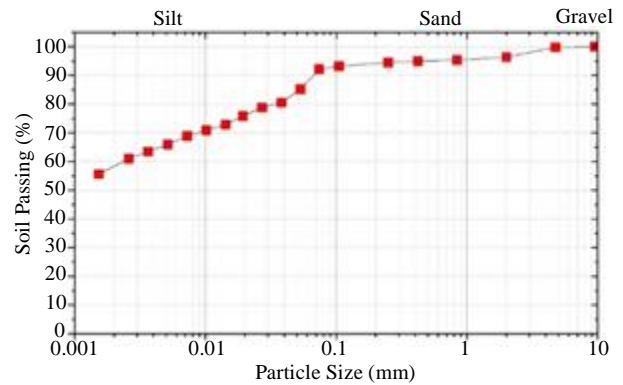


Fig. 5 Particle size distribution of black cotton soil

3.2. Physical and Mechanical Properties of Black Cotton Soil

The primary mechanical and physical characteristics of lime, silica sand, and untreated black cotton clay soil are compiled in Tables 2, and 3.

3.2.1. Particle Size Distribution

Figure 5 illustrates the distribution of particle sizes in the black cotton soil. Based on the characteristics exhibited from the tests, the soil was categorized under the AASHTO criteria as A-7-6 and ASTM D422-98 [23]. It was indicated that black cotton soil contained 3.44% gravel, 7.67% sand, 30% silt, and 58.30% clay [24].

3.3. Effect of Silica Sand and Lime Stabilization on the Consistency Limits of Black Cotton Soil

The percentage of silica sand rose from 0 to 12% by dry mass (Figure 6). As the amount of silica sand rose, the Plastic Limit (PL) and Liquid Limit (LL) both decreased. The best modification was achieved, as seen in (Figure 7), when 8% silica sand was added, and the dry mass lime percentage was raised from 0% to 8%, gradually decreasing the Plasticity Index (PI) to 2.31% from 30.39%. While Liquid Limit (LL) initially decreased slightly with lime proportions of 0-8%, Plastic Limit (PL) showed a small rise (Figure 7) enhancing soil consistency [25].

As silica sand content increased from 0% to 12%, this led to a decrease in linear shrinkage from 15.71% to 12.14% (Figure 6). Varying lime content from 0 to 8% further decreased linear shrinkage from 15.71% to 5.71% (Figure 7) [26].

As noted by [27], lime contributes to soil strength through cation exchange and pozzolanic reactions, forming cementitious compounds. The combination of silica sand and lime, therefore, facilitated the formation of cementitious

bonds, decreasing PI and improving consistency. This modification curbed soil expansion, which is suitable for road construction. Consequently, the study concludes that

combining 8% silica sand and 2% lime effectively modified the soil’s consistency for cost-effective road construction while curbing expansion and reducing shrinkage [28].

Table 2. Engineering properties of black cotton soil

Property	Value	Standard
Colour Observations	Dark Grey	
Moisture Content	8.07%	BS 1377-2,1990
Classification (AASHTO)	A-7-6	BS 1377-2-1990, ASTM D 4318
Plastic Limit (PL)	29.03%	
Plasticity Index (PI)	30.39%	
Liquid Limit (LL)	59.42%	BS 1377-2,1990
Linear Shrinkage	15.71%	ASTM D427 and BS 1377-2-1990
Free-Swell	110%	BS 1377-2,1990
Specific Gravity	2.23	BS 1377-2,1990
Maximum Dry Density	1.335g/cm ³	ASTM D698-00 a, BS 1377-4-1990
Optimum Moisture Content	28.0%	
Soaked CBR (4 Days Soaking)	1.41%	AASHTO T193-93, BS 1377:1990, ASTM D 4429/D1883
UCS	50.11 kPa	BS1377:1990, ASTMD2166/D2166M

Table 3. Specific gravity properties for black cotton soil, lime, and silica sand

Sample	Specific Gravity Value	Code Limits	Standard Code
Black Cotton	2.23	2.6- 2.75	ASTMD854-02, ASTM C128(2001), BS 1377-2,1990
Lime	2.32	2.0-2.3	BS 1377-2,1990
Silica Sand	2.66	2.55-2.75	ASTM C 128, (2001)

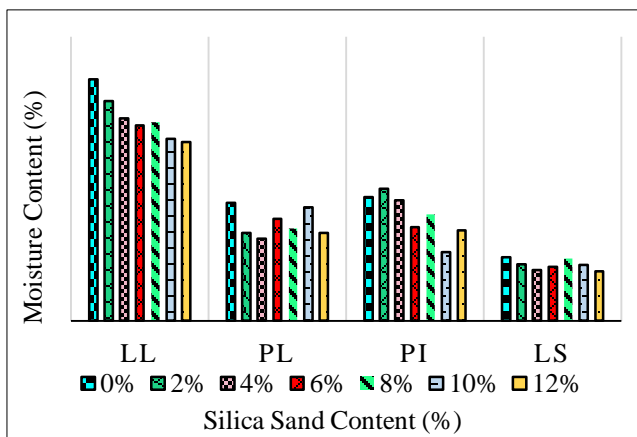


Fig. 6 Black cotton’s consistency limits when treated with silica sand content

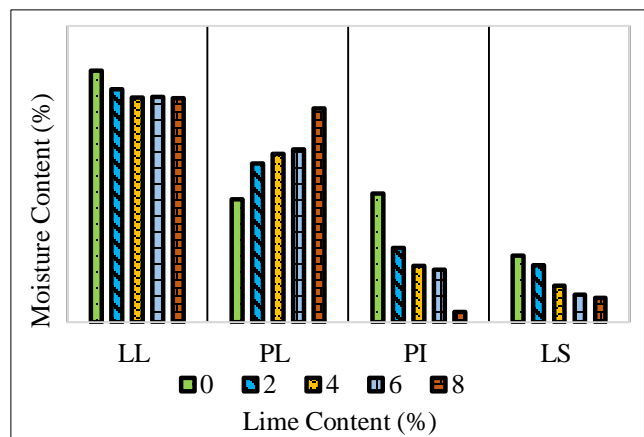


Fig. 7 Black cotton’s consistency limits when treated with 8% silica sand and different amounts of lime content

3.4. Effect of Silica Sand and Lime Stabilization on Free-Swell of Black Cotton Soil

The untreated black cotton soil exhibited a high free swell index of 110%, demonstrating its distinctive characteristics. However, the free swell was significantly reduced when silica sand concentration was increased from 0% to 12%, the range between 65% to 30%, as shown in (Figure 8) [29]. According to [30], a free swell index greater than 50% is considered very high. Furthermore, when 0% to 8% lime content was added to the optimum 8% silica sand, it further decreased the free swell, as depicted in (Figure 9).

This demonstrates the effectiveness of lime in addressing the problematic volume-change tendencies of the soil. Lime can interact with clay soils at a physicochemical level, leading to modifications in the microstructure of the clay. By incorporating silica sand and lime into the soil, they function as pore-fillers, preventing clay from swelling through the establishment of a static interaction between silica sand and clay particles.

Consequently, lime forms a protective coating around and reinforces the surfaces of clay particles. Additionally, the absorbed lime organics disrupt the structured water layer, leading to a denser arrangement of particles, as observed in [31]. These geotechnical additives prove highly effective in reducing swelling to a maximum of 50%, thus fulfilling the stability requirements specified in the Kenya road manual [36].

3.5. Effect of Silica Sand Lime Stabilization on Compaction of Black Cotton Soil

As shown in (Figure 10) Optimum Moisture Content (OMC) decreased while MDD increased with rising silica sand concentrations from 0 to 12%. On adding 8% silica sand as optimum and the lime content increased from 0% to 8%, the OMC decreased from 28% to 24% (Figure 11).

Nevertheless, as a result of incorporating 8% silica sand and 2% lime, the optimum result of compaction, MDD 1.378 gm/cc, and OMC 27.5% at 2% lime (Figure 11) as concluded. The decrease in OMC can be attributed to the hygroscopic nature of lime. In the context of soil stabilization, lime acts as a binding substance that enhances the cohesion and load-bearing capacity of soils. This is typical of silica sand and lime stabilization, as lime reacts with clay minerals, improving soil compaction and reducing the moisture content required for optimal compaction.

3.6. Effect of Silica Sand and Lime Stabilization on CBR of Black Cotton Soil

Black cotton soil’s CBR of 1.41% demonstrated that it was incredibly insufficient to be used as a road subgrade to withstand the demands of traffic loads. This discovery was likewise reported by [32]. An optimum of 6.9% was reached by adding 8% silica sand (Figure 12) [33]. This is still below

the typical minimum standard, as indicated according to [34-36]. Beyond 8% silica sand, the CBR started decreasing.

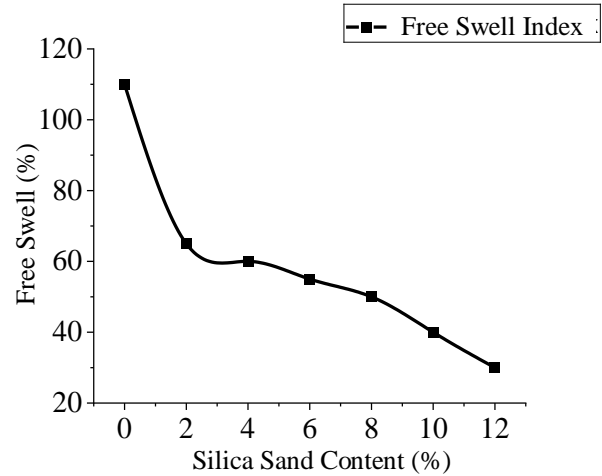


Fig. 8 Free swell of black cotton soil with silica sand content only

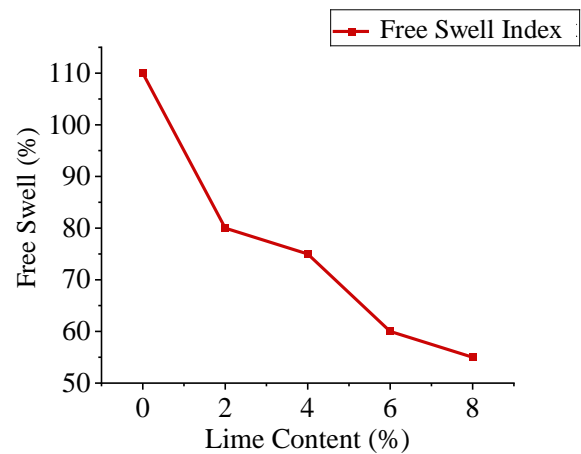


Fig. 9 Free swell of black cotton soil with 8% silica sand and varying lime content

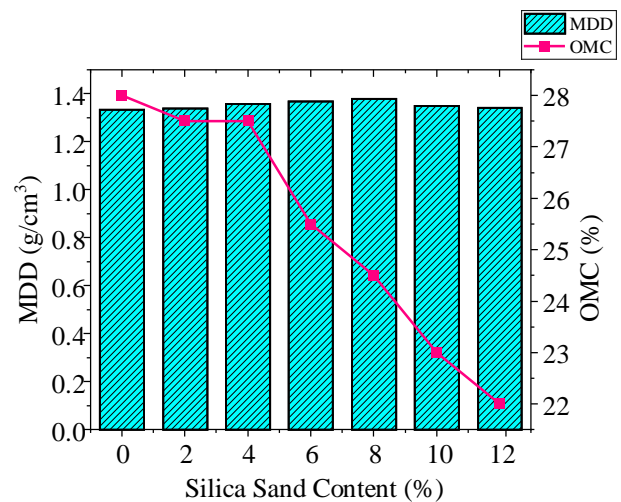


Fig. 10 OMC and MDD of black cotton only containing silica sands

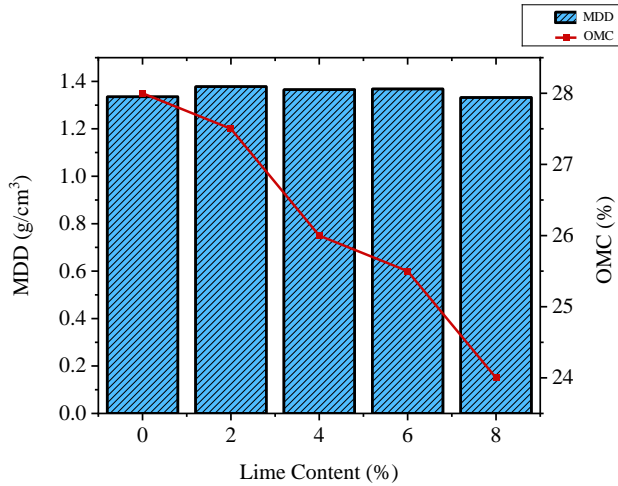


Fig. 11 OMC and MDD of black cotton treated through 8% silica sand and lime content

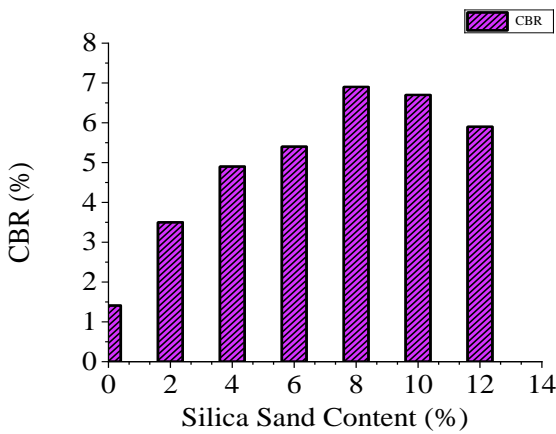


Fig. 12 CBR of black cotton soil containing only silica sand

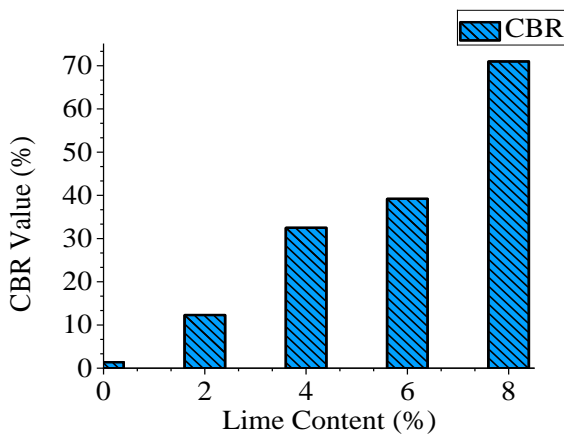


Fig. 13 CBR of black cotton treated with 8% silica sand and varying lime content

Adding 0 to 8% lime on an optimum of 8% silica sand. The complementary static interactions with silica sand and lime-treated clay minerals clarify the enhanced strength after

adding 2% lime. Modifying mineralogy and pore structure through physico-chemical mechanisms imparted by the optimized 8% silica sand and 2% lime treatment increased the CBR to 12.3% (Figure 13) load-bearing capacity was sufficiently improved to support traffic loads per design requirements.

3.7. Effect of Silica Sand and Lime Stabilization on UCS of Black Cotton Soil

The Unconfined Compressive Strength (UCS) of silica sand increased from 2 to 8 as the proportion of silica sand varied from 0 to 12% (Figure 14) as reported by [37]. However, the UCS values decreased for proportions of 10% and 12%.

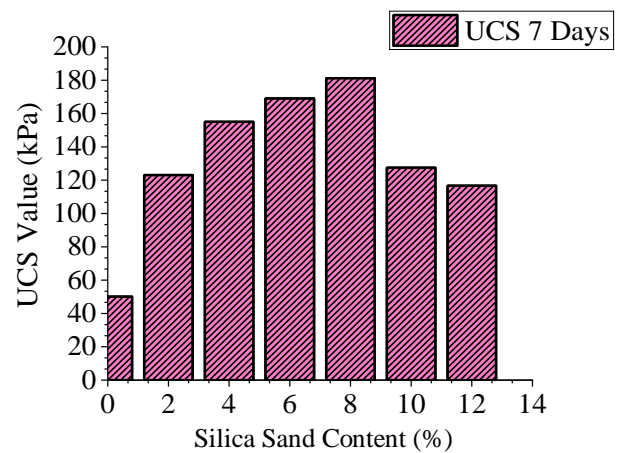


Fig. 14 UCS of black cotton soil treated with silica sand content

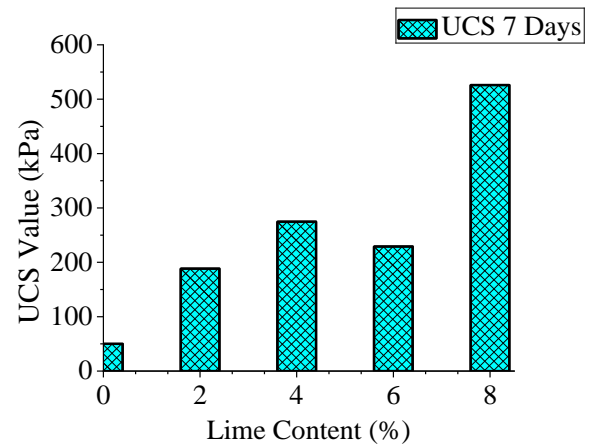


Fig. 15 UCS of black cotton treated with 8% silica sand and varying lime content

However, it was found that 8% silica sand was the optimal amount, and 181.23 kPa determined the treated soil's UCS value after seven days [38]. Similarly, an optimal proportion of 8% silica sand was achieved while maintaining a lime content ranging from 0 to 8% in black cotton soil (Figure 15), resulting in enhanced qualities of mechanical strength. With a

rise in lime content, the soil exhibited enhanced cohesive properties, leading to a significant increase in axial strain. This indicates that the soil became very stiff, as classified according to [39, 40]. The substantial improvement in strength observed with the reaction can be linked to a higher silica sand content between silica, calcium ions from lime, and clay minerals.

4. Conclusion

This study aimed to evaluate the performance of black cotton soil stabilized with silica sand and lime as a subgrade material for road construction. The subsequent conclusions are derived from the results obtained in this study:

- The effect of silica sand alone in black cotton soil is significant in linear shrinkage. However, adding lime does improve the black cotton soil's plastic index. Further, the free swell index can be reduced to a very high degree by adding 8% silica sand in black cotton soil.
- The addition of 8% silica sand, which was determined to be the optimal proportion, along with 2% lime, resulted in an enhancement in contrast to stabilized soil with silica sand and lime in the range of 4% to 8% lime content, the

maximum dry density and a decrease in the ideal moisture content increased stabilized black cotton soil.

- The addition of 8% silica sand and 2% lime to black cotton soil leads to 12.03% and 188.39 kPa CBR and UCS values, respectively. Thus, increase in strength.
- The addition of silica sand as a co-stabilizer with lime has a profound effect on the California Bearing Ratio and unconfined compressive strength of black cotton soil. An optimum value of 8% silica sand and 2% lime was realized in this study.

Funding Statement

The authors would like to express their gratitude to the African Union for providing financial support for this research.

Acknowledgments

The authors extend their appreciation to the Pan African University, Institute for Basic Science, Technology, and Innovation at Jomo Kenyatta University of Agriculture and Technology in Nairobi, Kenya.

References

- [1] Luqi Wang et al., "The Impacts of Transportation Infrastructure on Sustainable Development: Emerging Trends and Challenges," *International Journal of Environmental Research and Public Health*, vol. 15, no. 6, pp. 1-24, 2018. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [2] Esdras Ngezahayo, Michael Burrow, and Gurmel Ghataora, "Rural Roads - Roles, Challenges and Solutions for Sub-Saharan Africa's Sustainable development," *International Journal of Latest Engineering and Management Research*, vol. 4, no. 10, pp. 70-79, 2019. [[Google Scholar](#)] [[Publisher Link](#)]
- [3] Ramakrishna Bag, and Ahsan Rabbani, "Effect of Temperature on Swelling Pressure and Compressibility Characteristics of Soil," *Applied Clay Science*, vol. 136, pp. 1-7, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [4] Bournebe Baimourne, Richard Ocharo Onchiri, and Joseph Ng'ang'a Thuo, "Investigation on the Suitability of High Clay Lateritic Soils Stabilized with Cement and Rice Husk Ash for Use in Road Base Construction: A Case Study of Juja Town," *International Journal of Engineering Trends and Technology*, vol. 71, no. 2, pp. 121-128, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [5] M.R. Asgari, A. Baghebanzadeh Dezfouli, and M. Bayat, "Experimental Study on Stabilization of a Low Plasticity Clayey Soil with Cement/Lime," *Arabian Journal of Geosciences*, vol. 8, pp. 1439-1452, 2015. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [6] Maryam Naeimi, and Abdolhosein Haddad, "Environmental Impacts of Chemical and Microbial Grouting," *Environmental Science and Pollution Research*, vol. 27, pp. 2264-2272, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [7] D.S. Vijayan, and D. Parthiban, "Effect of Solid Waste Based Stabilizing Material for Strengthening of Expansive Soil- A Review," *Environmental Technology & Innovation*, vol. 20, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [8] K.A. Nadgouda, and R.A. Hedge, "The Effect of Lime Stabilization on Properties of Black Cotton Soil," *Indian Geotechnical Conference*, pp. 511-514, 2010. [[Google Scholar](#)]
- [9] Larry Pax Chegbeleh, and Frank Siaw Ackah, "Chemical Stabilization of Black Cotton Clay and Laterite Soil Using Drycon Powder for Suitability as Construction Materials," *Journal of Geography, Environment and Earth Science International*, vol. 24, no. 4, pp. 29-39, 2020. [[CrossRef](#)] [[Publisher Link](#)]
- [10] Worku Janka Negawo et al., "Lime-Stabilisation of High Plasticity Swelling Clay from Ethiopia," *European Journal of Environmental and Civil Engineering*, vol. 23, no. 4, pp. 504-514, 2019. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [11] M. Adams Joe, and A. Maria Rajesh, "Soil Stabilization Using Industrial Waste and Lime," *International Journal of Scientific Research Engineering & Technology*, vol. 4, no. 7, pp. 799-805, 2015. [[Google Scholar](#)] [[Publisher Link](#)]
- [12] Adedeji, "Lime-Treated Soil Construction Manual: Lime Stabilization & Lime Modification," *Bulletin 326*, 2004. [[Google Scholar](#)] [[Publisher Link](#)]
- [13] Olumide Moses Ogunipe, "An Investigation into the Use of Lime-Stabilized Clay as Subgrade Material," *International Journal of Scientific & Technology Research*, vol. 2, no. 10, pp. 82-86, 2013. [[Google Scholar](#)]

- [14] G.A. Duvuna, and A. Ayuba, "Assessment of the Chemical and Physical Properties of Silica Sand for Glass Making," *Journal of Engineering and Technology*, vol. 8, no. 2, pp. 46-49, 2013. [[Google Scholar](#)] [[Publisher Link](#)]
- [15] G.A. Duvuna, and A. Ayuba, "A Study on Silica Sand Quality in Yazaram and Mugulbu Deposits for Glass Making," *Nigerian Journal of Technology*, vol. 34, no. 1, pp. 109-112, 2015. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [16] E.M. Alemaka, A.D. Garkida, and A.M. Abdullahi, "Characterization of Makkoda Silica Sand Deposit in Kano State Northwest Nigeria for Use in Glass Manufacturing Characterization of Makkoda Silica Sand Deposit in Kano State Northwest Nigeria for Use in Glass Manufacturing," *ATBU Journal of Science, Technology and Education*, vol. 9, no. 2, 2021. [[Google Scholar](#)] [[Publisher Link](#)]
- [17] A.A. Shuaibu et al., "An Experimental Study on the Performance of Bituminous Concrete Mixtures with Silica Sand as Filler Replacement," *Arid Zone Journal of Engineering, Technology and Environment*, vol. 17, no. 4, pp. 453-468, 2021. [[Google Scholar](#)] [[Publisher Link](#)]
- [18] Nicholas Ogbonna Anaekwe, and Yusuf Mi kailu Hassan, "Chemical Evaluation of the Glass Making Potentials of Silica Sand Deposits Along Cross River in Cross River State, South-East of Nigeria," *European Journal of Engineering and Technology Research*, vol. 2, no. 6, pp. 12-17, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [19] Yongzhen Cheng, and Xiaoming Huang, "Effect of Mineral Additives on the Behavior of An Expansive Soil for Use in Highway Subgrade Soils," *Applied Sciences*, vol. 9, no. 1, pp. 1-14, 2019. [[CrossRef](#)] [[Publisher Link](#)]
- [20] Dharmendra Barman, and Sujit Kumar Dash, "Stabilization of Expansive Soils Using Chemical Additives: A Review," *Journal of Rock Mechanics and Geotechnical Engineering*, vol. 14, no. 4, pp. 1319-1342, 2022. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [21] Ramalingam Malathy et al., "Use of Industrial Silica Sand as a Fine Aggregate in Concrete-An Explorative Study," *Buildings*, vol. 12, no. 8, pp. 1-26, 2022. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [22] Ozlem Cizer et al., "Phase and Morphology Evolution of Calcium Carbonate Precipitated by Carbonation of Hydrated Lime," *Journal of Materials Science*, vol. 47, pp. 6151-6165, 2012. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [23] Alemineh Sorsa, Sanjaya Senadheera, and Yoseph Birru, "Engineering Characterization of Subgrade Soils of Jimma Town, Ethiopia, for Roadway Design," *Geosciences*, vol. 10, no. 3, pp. 1-17, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [24] Kolawole J. Osinubi, Adrian O. Eberemu, and Olusegun B. Akinmade, "Evaluation of Strength Characteristics of Tropical Black Clay Treated with Locust Bean Waste Ash," *Geotechnical and Geological Engineering*, vol. 34, no. 2, pp. 635-646, 2016. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [25] Alemineh Sorsa, and Elmer Agon, "Lime Stabilization of Expansive Clay Soil of Jimma Town, Ethiopia," *Civil Engineering Infrastructures Journal*, vol. 55, no. 2, pp. 211-222, 2022. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [26] Samuel Akinlabi Ola et al., "The Geology and Geotechnical Properties of the Black Cotton Soils of Northeastern Nigeria," *Engineering Geology*, vol. 12, pp. 375-391, 1978. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [27] Shivesh Kumar et al., "Effect of Lime (Content & Duration) on Strength of Cohesive Soil," *International Research Journal of Engineering and Technology*, vol. 6, no. 5, pp. 198-205, 2019. [[Google Scholar](#)] [[Publisher Link](#)]
- [28] S. Srikanth Reddy, A.C.S.V. Prasad, and N. Vamsi Krishna, "Lime-Stabilized Black Cotton Soil and Brick Powder Mixture as Subbase Material," *Advances in Civil Engineering*, vol. 2018, pp. 1-6, 2018. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [29] Manal O. Suliman, and Abdulrazzaq Jawish Alkherret, "Using Fine Silica Sand and Granite Powder Waste to Control Free Swelling Behavior of High Expansive Soil," *Modern Applied Science*, vol. 15, no. 1, pp. 53-62, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [30] Sudhakar M. Rao, *Identification and Classification of Expansive Soils, Expansive Soils*, CRC Press, pp. 27-36, 2006. [[Google Scholar](#)] [[Publisher Link](#)]
- [31] Soewignjo Agus Nugroho et al., "Effects of High Plasticity and Expansive Clay Stabilization with Lime on UCS Testing in Several Conditions," *Journal of the the Civil Engineering Forum*, vol. 7, no. 2, pp. 147-154, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [32] Niyomukiza John Bosco et al., "Use of Waste Glass Powder in Improving the Properties of Expansive Clay Soils," *Global NEST Journal*, vol. 25, no. 3, pp. 139-145, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [33] Ika Puji Hastuty, and Agung Hartawan, "Unconfined Compressive Strength and California Bearing Ratio Test on Clay Stabilization Using Silica Sand," *IOP Conference Series: Materials Science and Engineering*, vol. 1122, pp. 1-7, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [34] E. Mina, R.I. Kusuma, and N. Ulfah, "Utilization of Steel Slag and Fly Ash in Soil Stabilization and Their Effect to California Bearing Ratio (CBR) Value. (Case Study: Kp. Kadusentar Road Medong Village Mekarjaya Subdistrict Pandeglang District)," *IOP Conference Series: Materials Science and Engineering*, vol. 673, pp. 1-8, 2019. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [35] H. D. Mac-Eteli, and S. Sopakirite, "Experimental Analysis on the Effect of Calcination on the Index and Engineering Properties of Clay Soil," *Saudi Journal of Civil Engineering*, vol. 5, no. 6, pp. 133-138, 2021. [[Google Scholar](#)] [[Publisher Link](#)]
- [36] Republic of Kenya, Ministry of Transport and Communication, Standard Specification for Road and Bridge Construction, 1986. [Online]. Available: <https://kenha.co.ke/wp-content/uploads/2023/01/Standard-Specification-for-Road-Bridge-Construction-1986.pdf>
- [37] A.S.S. Gunarti et al., "Unconfined Compression Strength of Soil Using Silica Sand Waste and Dust Sand Foundry as A Stabilizer," *Journal of Physics: Conference Series*, pp. 1-6, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]

- [38] Karanbir Singh Randhawa, Rajiv Chauhan, and Raman Kumar, "An Investigation on the Effect of Lime Addition on UCS of Indian Black Cotton Soil," *Materials Today: Proceedings*, vol. 50, no. 5, pp. 797-803, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [39] Neeraj Kumar Sharma, S.K. Swain, and Umesh C. Sahoo, "Stabilization of a Clayey Soil with Fly Ash and Lime: A Micro Level Investigation," *Geotechnical and Geological Engineering*, vol. 30, no. 5, pp. 1197-1205, 2012. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [40] Nooraien Hashmie et al., "Utilisation of Recycled Glass Powder for the Stabilization of Black Cotton Soil by Alkali Activation," *IOP Conference Series: Materials Science and Engineering*, vol. 955, no. 1, pp. 1-6, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]